

Drilling high aspect ratio holes by femtosecond laser filament with aberrations

Manshi WANG, Zhiqiang YU, Nan ZHANG (✉), Weiwei LIU

Institute of Modern Optics, Nankai University, Tianjin Key Laboratory of Micro-scale Optical Information Science and Technology, Tianjin 300350, China

© Higher Education Press 2021

Abstract A near-infrared femtosecond laser is focused by a 100 mm-focal-length plano-convex lens to form a laser filament, which is employed to drill holes on copper targets. By shifting or rotating the focusing lens, additional aberration is imposed on the focused laser beam, and significant influence is produced on the aspect ratio and cross-sectional shape of the micro-holes. Experimental results show that when proper aberration is introduced, the copper plate with a thickness of 3 mm can be drilled through with an aspect ratio of 30, while no through-holes can be drilled on 3-mm-thickness copper plates by femtosecond laser with minimized aberration. In addition, when femtosecond laser filament with large astigmatism is used, micro-holes that had a length to width ratio up to 3.3 on the cross-section are obtained. Therefore, the method proposed here can be used to fabricate long oval holes with high aspect ratios.

Keywords femtosecond laser, aberration, drilling, high aspect ratio

1 Introduction

Micro-holes with high aspect ratios fabricated on metallic targets are highly demanded in engine manufacturing, biomedical applications, and other practical fields. Electrical discharge machining [1], electrochemical machining [2], and laser machining [3] are major prevailing methods for metal hole drilling. Among these methods, femtosecond laser drilling has its unique advantages. The femtosecond laser can accomplish energy deposition before the establishment of the electron-phonon thermodynamic equilibrium and therefore achieve fewer thermal

defects, smaller heat-affected zone, and higher fabrication precision [4,5] than long-pulse laser fabrication. Accompanied with magnetic field, femtosecond laser could also fabricate some high aspect-ratio micro-structures for dynamic modulation of optical and mechanical properties of textured surfaces [6,7]. Moreover, femtosecond laser with peak power larger than the critical power P_{cr} for self-focusing may undergo the subtle balancing among the Kerr effect induced self-focusing, the plasma-induced defocusing and the propagation induced diffraction, forming a plasma channel called laser filament [8]. Laser filament is a plasma channel with a high optical intensity of $\sim 10^{13}$ W/cm² [9,10], sustaining orders of magnitude longer than the Rayleigh length, which suggests that a filament is a competent tool for high aspect ratio hole drilling [11,12]. Bessel and Bessel-like beam with long focal range generated by the axicon and axilens are potent tools used for deep hole drilling [13–15], while the processing target needs to be transparent at the laser's wavelength so that the sidelobes can penetrate through the target to form a long focal-length beam. Contrastingly, the femtosecond filament sustained by the dynamic balance among the Kerr effect induced self-focusing, the plasma's defocusing, and the beam diffraction in the paraxial region would be an effective method for deep hole drilling in opaque materials.

A major problem when using femtosecond laser filament to drill high aspect ratio holes is the large taper, induced by the decrease of laser energy coupling efficiency as the increase of hole depth [16,17]. Trepanning drilling can, in principle, eliminate the hole taper. Nevertheless, in practice, trepanning drilling expands hole diameter and thus decreases the aspect ratio and increases processing time. Several studies have demonstrated that aberration introduced before laser focusing can modify the diameter, length, and spatial distribution of laser filaments [18–21], i.e., modify the drill tool's 3D shape. However, so far, there have been few discussions about the effects of aberration on laser filament drilling.

This study is intended to investigate the effects of aberration on laser filament drilling. Here, the aberration effect, which is commonly a hope-to-diminished factor in the laser drilling process, was quantitatively introduced into the femtosecond laser beam by shifting or rotating the focusing lens [22]. Experimental results show that the aberration-modified laser filament can not only drill almost zero tapered holes but also drill holes with different shapes, such as round and oval holes. This research serves as a basis for future studies and enhances our understanding of the role of aberrated laser filamentation in high aspect ratio hole drilling.

2 Material and methods

Figure 1 depicts the top view of the experimental setup for femtosecond laser drilling. A Ti:sapphire femtosecond laser amplifier system (Legend Elite, Coherent Inc.) is employed to generate an 800 nm, 35 fs, 1 kHz laser pulse train. Laser average power is modulated in the range of 0.14–1.1 W by inserting different neutral density filters, while the shortest pulse duration near the laser focus is maintained by adjusting the pulse compressor of the femtosecond laser amplifier system. The diameter of the laser beam incident on the focusing lens is 10 mm. The laser beam is focused by a plano-convex lens with a focal length of 100 mm and a central thickness of 3.6 mm to form an optical filament. The laser filament is an air plasma channel along Z-axis. To introduce the aberration to the laser filament, the focusing lens is mounted on a one-dimensional translation stage and a rotation stage to achieve lens shifting along X-axis and lens rotating about Y-axis. Lens offset along X-axis and rotation angle φ about Y-axis are used to quantify the lens movement relative to the principal axis of the optical setup. The workpiece, i.e., the copper plate, is placed at different positions along Z-axis during the hole drilling process. Finally, hole features are investigated by an optical microscope (Olympus, BX51). Copper plates used in experiments are 20 mm ×

20 mm in size, 0.5 and 3 mm in thickness, mounted on a three-dimensional translation stage. Copper has high electrical and thermal conductivity, thus widely used in industrial for precision manufacturing.

In experiments, high aspect ratio holes are drilled respectively by the focused laser beam with minimized aberration (see the dash-line frame in Fig. 1) or modulated external aberration (see the dot-dash-line frame in Fig. 1).

3 Results and discussion

3.1 Characteristics of holes drilled by laser filament with minimized aberration

In this subsection and the following parts of this paper, D_x and D_y are respectively used to evaluate the hole diameters along X and Y axis, which is schematically shown in Fig. 2(a). Defocusing amount (DA) indicates the distance between the top surface of the target and the geometrical plane of the focusing lens. DA is positive when the top target surface is closer to the focusing lens than the geometrical focal plane. Figure 2(a) presents the optical microscopic images of the top surface after drilling. It is seen from Figs. 2(b) and 2(c) that D_x and D_y both reach the minimum at DA = 0 when laser filament with minimized aberration is used. The diameters of holes are nearly independent of the laser power in the range of 0.2–0.9 W. As shown in Fig. 2(d), holes at the top surface of the target have good symmetry (D_x/D_y). Other parameters of holes fabricated by femtosecond laser with additional artificial aberrations are presented in the following sections.

3.2 Characteristics of holes drilled by laser filament with lens shifting induced aberration

As mentioned above, lens shifting was quantified by the lens offset along X-axis. It is seen from Figs. 3(a) and 3(b) that D_x and D_y have individual dependences on the lens offset. As the offset value increases from 0 to 5 mm, the

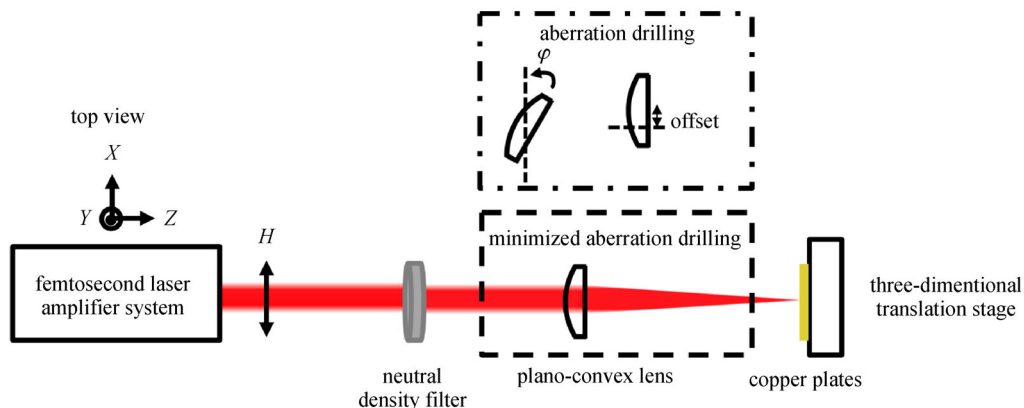


Fig. 1 Top view of experimental setup for femtosecond laser drilling copper plates

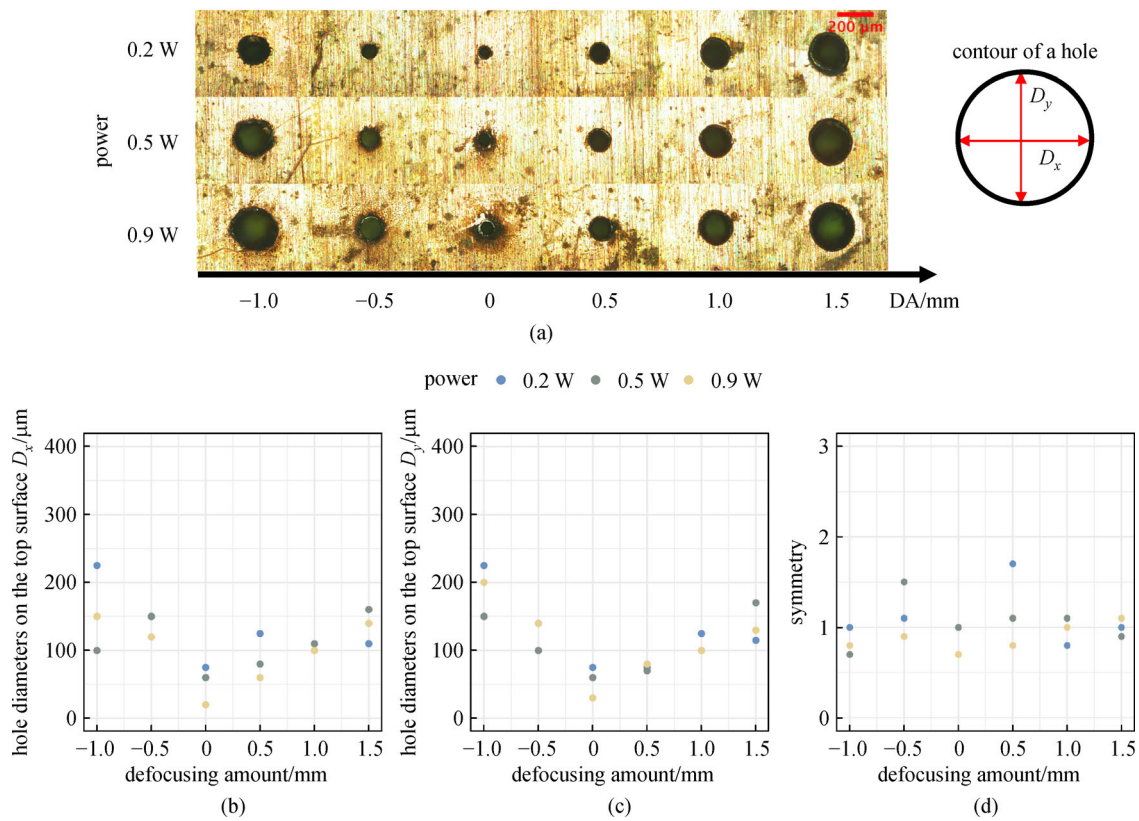


Fig. 2 (a) Optical microscopic images of the drilled top surface of copper plates. Dependences of the top surface hole diameters D_x (b), D_y (c), and hole symmetry (d) on the target defocusing amount. The copper plate has a thickness of 0.5 mm

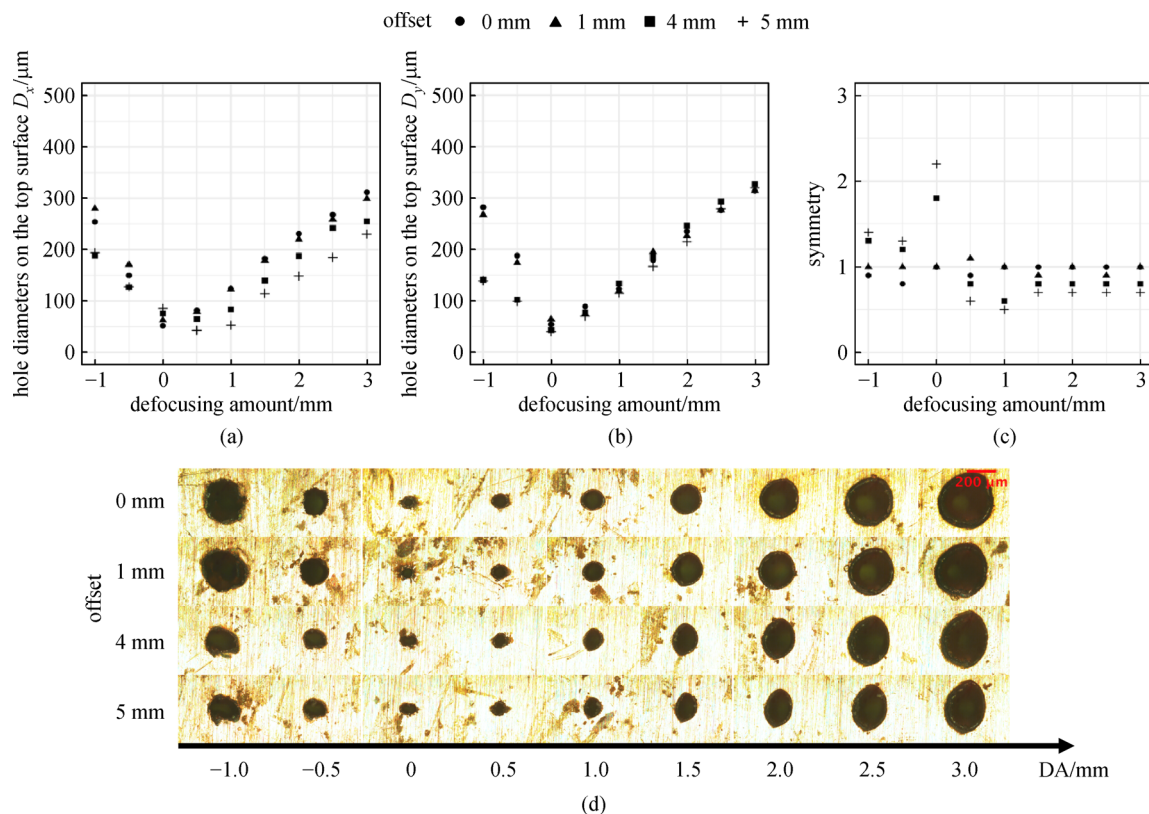


Fig. 3 Dependences of top surface D_x (a), D_y (b), and symmetry (c) on the lens offset and target defocusing amount. (d) Optical microscopic images of holes on the top surface. The copper plate has a thickness of 0.5 mm. These through-holes are drilled by femtosecond laser with an average power of 0.5 W

position of minimal D_x moves from the geometrical focal plane to the position at $DA = 0.5$ mm. However, no such movement exists for D_y , and D_y seems independent on the aberration introduced by lens shifting along X -axis for $DA > 0$. In Fig. 3(c), it is seen that asymmetric holes are fabricated when different offset value is introduced, and the major axis of the hole alters when the sign of the defocusing amount changes. Figure 3(d) shows the optical microscopic images of holes on the top target surface drilled by femtosecond laser with lens shifting in varying degrees.

The aspect ratio and taper are two key parameters to evaluate hole quality, shown in Fig. 4. Since the hole diameter on the top surface is always larger than that on the bottom surface, the aspect ratio is defined as the ratio of the hole depth to the hole average diameter D_{top} on the top surface and D_{top} can be calculated by

$$D_{top} = \frac{D_x + D_y}{2}. \quad (1)$$

Taper in degree is calculated by

$$\theta = \arctan \frac{D_{top} - D_{btm}}{2L}, \quad (2)$$

where D_{btm} is the average hole diameter on the bottom surface, L is the hole depth. Data points in Figs. 4(a) and 4(b) respectively show a peak and a valley near $DA = 0$, indicating that both high aspect ratio and small taper appear at $DA = 0$. From Figs. 4(a) and 4(b), lens offset-induced aberration cannot increase the aspect ratio but can make the hole taper closer to zero for $DA = 0 - 0.5$ mm.

3.3 Characteristics of holes drilled by femtosecond laser filament with lens rotation induced aberration

In addition, aberration can also be induced by rotating the focusing lens. In this section, the lens is rotated in the range of $0^\circ - 8^\circ$, and different aberrations are introduced on the

femtosecond laser. In Figs. 5(a) and 5(b), it is seen that the minimal diameter appears at different defocusing amounts for different rotation angles. It should be noted that a large rotation angle may deteriorate the symmetry of holes, as shown in Fig. 5(c). Circular holes or oval holes can be drilled at a certain lens orientation, as shown in Fig. 5(d).

Figure 6 shows the aspect ratio and the averaged taper of holes fabricated in Fig. 5. A remarkable observation is that the data points show a more gentle slope at $\varphi = 5^\circ$ and $\varphi = 8^\circ$ than that at $\varphi = 0^\circ$, which indicates the filament is modified along Z -axis by rotation-induced aberration. Modified filament has a flexible machining range along Z -axis, which is the desired tool in deep hole drilling. Since the shape of holes on the X - Y plane is deformed (see Fig. 5(d)) due to the aberration induced by lens rotation, it is considered that calculating the taper respectively for the X and Y directions can better exhibit the taper reduction effect by the aberration. The calculated results are shown in Figs. 7(a) and 7(b). Tapers on the X and Y directions are calculated by

$$\theta_X = \arctan \frac{D_{topX} - D_{btmX}}{2L},$$

and

$$\theta_Y = \arctan \frac{D_{topY} - D_{btmY}}{2L}.$$

The obvious distinction in the variation tendency exists for tapers along X and Y directions, caused by the asymmetric external aberration on the X and Y directions. It can be seen from Fig. 7 that setting the rotation angle of the lens to be 5° can lead to a smaller θ_Y compared with those without introducing aberrations. It is also found that rotating the focusing lens can counteract the increasing tendency of θ_X for larger defocusing amount. For the lens rotation angle of 2° and defocusing amount of 0.5 mm, tapers on both the X and Y directions are close to zero, which is much smaller than that without aberrations.

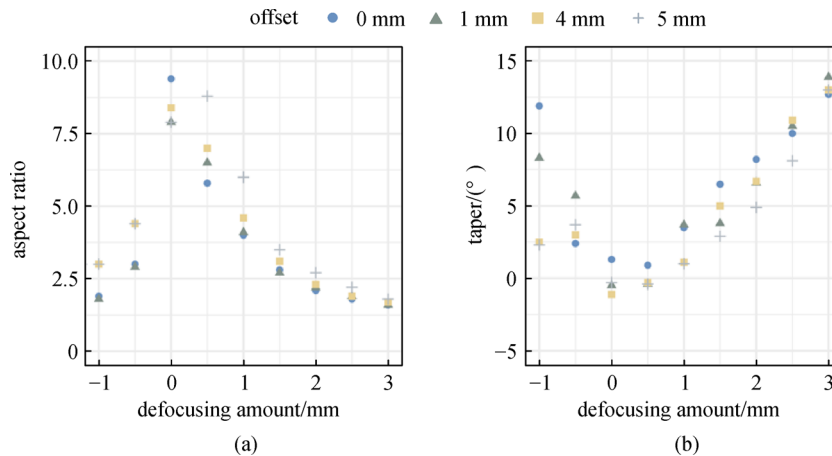


Fig. 4 Characteristics of through holes drilled by femtosecond laser filament with lens shifting. Aspect ratio (a) and taper (b) of holes in 0.5 mm-thickness copper plates are presented. The lens shifting amount ranges from 0 to 5 mm. The average laser power is 0.5 W

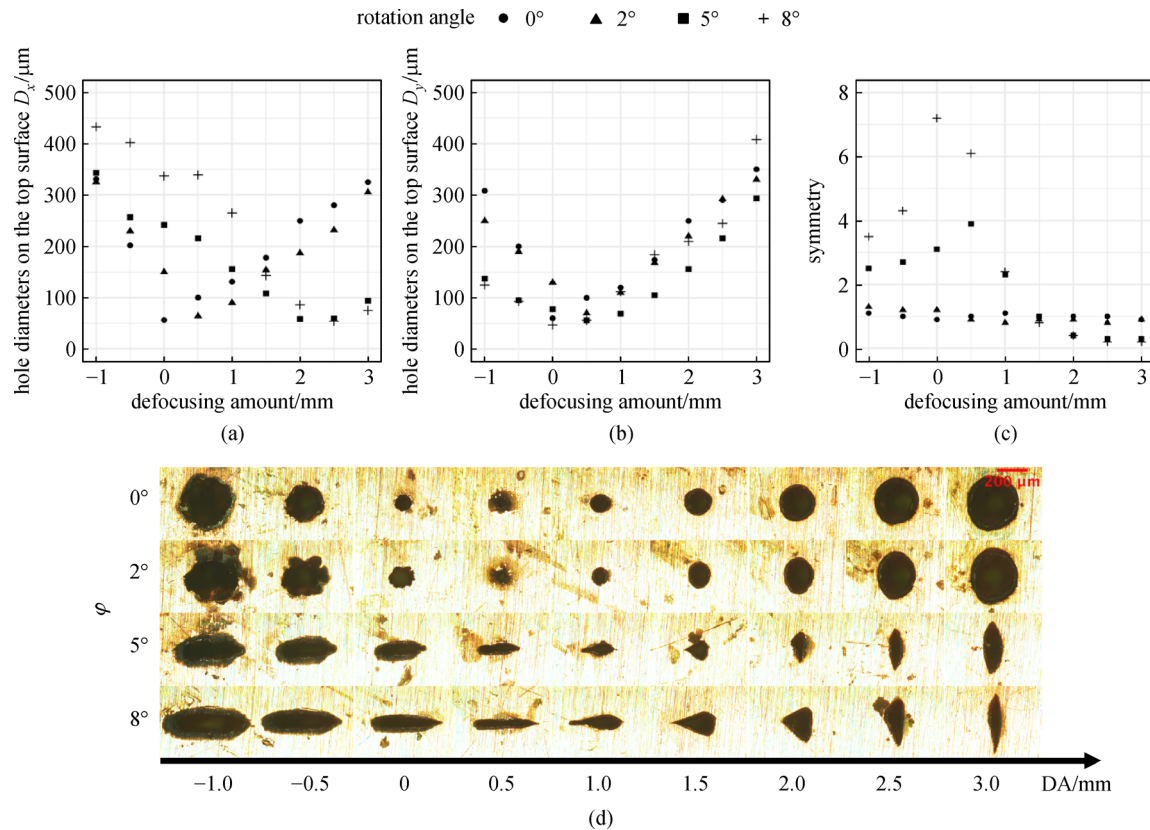


Fig. 5 Dependences of the top-surface hole diameters D_x (a), D_y (b), and symmetry (c) on the lens rotation angle and target defocusing amount. (d) Optical microscopic images of holes on the top target surface. The copper plate has a thickness of 0.5 mm. These through-holes are drilled by femtosecond laser with an average power of 0.5 W

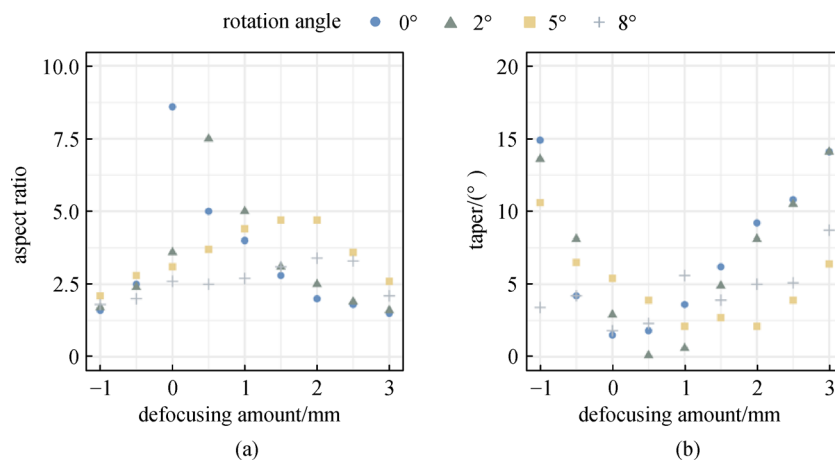


Fig. 6 Characteristics of through holes drilled by femtosecond laser filament with lens rotation. Aspect ratio (a) and taper (b) of holes in 0.5 mm-thickness copper plate are presented. The lens rotation angle ranges from 0° to 8°. The average laser power is 0.5 W

Figures 4(b) and 6(b) indicate that a smaller taper can be achieved by shifting or rotating the focusing lens, which is more valuable than a high aspect ratio for fabricating deeper holes. For laser drilling, especially drilling through holes on a thick metallic sample, deposited laser energy decreases as the increase of hole depth, which causes the enlargement of the top surface hole diameter or the

shrinkage of the bottom surface hole diameter. According to the experiment results in this paper, the taper can be decreased by the lens rotating from 2° to 8°. Lens rotation as a taper reducing method is more economical and simpler than trepanning [23], helical drilling [24], and chemical post-process [25].

Finally, a femtosecond laser beam with 0.9 W average

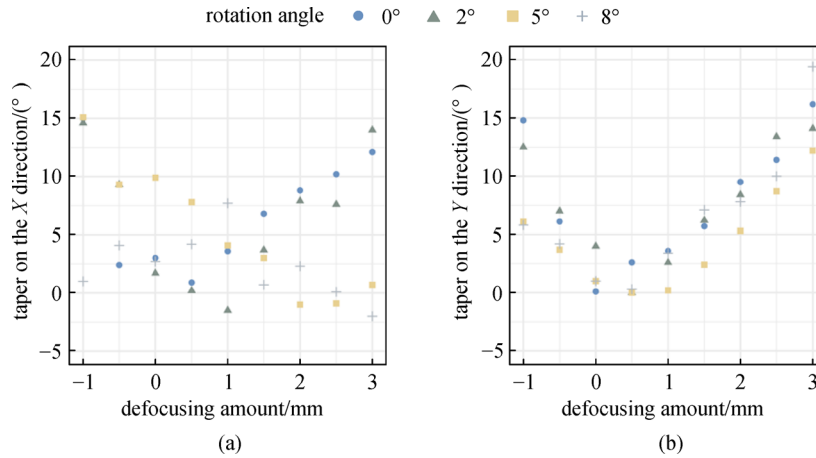


Fig. 7 Hole tapers for the X direction (a) and Y direction (b) on the 0.5-mm-thickness copper plate. The lens rotation angle ranges from 0° to 8° . The average laser power is 0.5 W

Table 1 Characteristics of holes on 3 mm copper plate at DA = 1.5 mm

	aspect ratio	taper	symmetry	drilling result
offset = 0, $\varphi = 0^\circ$			1.0	blind holes*
offset = 4 mm, $\varphi = 0^\circ$	25.2	0.4°	1.0	through holes
offset = 0, $\varphi = 5^\circ$	34.1	0.2°	0.7	through holes

Notes: * For blind holes, aspect ratio and taper have not been computed.

power is employed to drill a 3 mm thick copper plate. Only blind holes can be drilled by femtosecond laser with minimized aberration. However, through-holes can be drilled by focused femtosecond laser when the focusing lens is shifted by a specific amount or rotated by a specific angle. The optimal drilling parameters and drilling results are listed in Table 1.

4 Conclusions

This study investigates the aberration's effect on laser filament drilling. Aberration is artificially introduced to the laser filament by shifting or rotating the focusing lens, and laser filaments with diverse aberrations are used to drill holes on copper targets. The experimental results indicate that laser filament with specified aberration can drill through holes with larger aspect ratio compared with those drilled by laser filament with minimized aberration. A 3-mm-depth through-hole with an aspect ratio larger than 30 can be drilled on the copper plate by laser filament with specified aberration. In addition, hole taper can be reduced by the lens shifting and rotation-induced aberration. These findings suggest that the focusing laser beam with aberration is a promising tool in drilling high aspect ratio holes on metallic targets.

Acknowledgements This work was supported by the National Key Research and Development Program (No. 2018YFB0504400).

References


1. Prakash V, Kumar P, Singh P, Hussain M, Das A, Chattopadhyaya S. Micro-electrical discharge machining of difficult-to-machine materials: a review. *Proceedings of the Institution of Mechanical Engineers. Part B, Journal of Engineering Manufacture*, 2019, 233 (2): 339–370
2. Zeng Z, Wang Y, Wang Z, Shan D, He X. A study of micro-EDM and micro-ECM combined milling for 3D metallic micro-structures. *Precision Engineering*, 2012, 36(3): 500–509
3. Schaaf P. *Laser Processing of Materials: Fundamentals, Applications and Developments*. New York: Springer, 2010
4. Zhang H, Di J, Zhou M, Yan Y. A comparison in laser precision drilling of stainless steel 304 with nanosecond and picosecond laser pulses. *Chinese Journal of Mechanical Engineering*, 2014, 27(5): 972–977
5. Kling R, Dijoux M, Romoli L, Tantussi F, Sanabria J, Mottay E. Metal microdrilling combining high power femtosecond laser and trepanning head. In: *Proceedings of Laser-based Micro- and Nanopackaging and Assembly VII*. San Francisco: SPIE, 2013, 86080F
6. Jiang S, Hu Y, Wu H, Zhang Y, Zhang Y, Wang Y, Zhang Y, Zhu W, Li J, Wu D, Chu J. Multifunctional janus microplates arrays actuated by magnetic fields for water/light switches and bio-inspired assimilatory coloration. *Advanced Materials*, 2019, 31(15): e1807507
7. Zhu S, Bian Y, Wu T, Chen C, Jiao Y, Jiang Z, Huang Z, Li E, Li J, Chu J, Hu Y, Wu D, Jiang L. High performance bubble

- manipulation on ferrofluid-infused laser-ablated microstructured surfaces. *Nano Letters*, 2020, 20(7): 5513–5521
8. Braun A, Korn G, Liu X, Du D, Squier J, Mourou G. Self-channeling of high-peak-power femtosecond laser pulses in air. *Optics Letters*, 1995, 20(1): 73–75
 9. Kasparian J, Sauerbrey R, Chin S. The critical laser intensity of self-guided light filaments in air. *Applied Physics. B, Lasers and Optics*, 2000, 71(6): 877–879
 10. Xu Z J, Liu W, Zhang N, Wang M W, Zhu X N. Effect of intensity clamping on laser ablation by intense femtosecond laser pulses. *Optics Express*, 2008, 16(6): 3604–3609
 11. Schwarz J, Diels J C. UV filaments and their application for laser-induced lightning and high-aspect-ratio hole drilling. *Applied Physics. A, Materials Science & Processing*, 2003, 77(2): 185–191
 12. Kiselev D, Woeste L, Wolf J P. Filament-induced laser machining (FILM). *Applied Physics. B, Lasers and Optics*, 2010, 100(3): 515–520
 13. Wang Z, Jiang L, Li X, Wang A, Yao Z, Zhang K, Lu Y. High-throughput microchannel fabrication in fused silica by temporally shaped femtosecond laser Bessel-beam-assisted chemical etching. *Optics Letters*, 2018, 43(1): 98–101
 14. He F, Yu J, Tan Y, Chu W, Zhou C, Cheng Y, Sugioka K. Tailoring femtosecond 1.5- μm Bessel beams for manufacturing high-aspect-ratio through-silicon vias. *Scientific Reports*, 2017, 7(1): 40785
 15. Pan D, Xu B, Liu S, Li J, Hu Y, Wu D, Chu J. Amplitude-phase optimized long depth of focus femtosecond axilens beam for single-exposure fabrication of high-aspect-ratio microstructures. *Optics Letters*, 2020, 45(9): 2584–2587
 16. Leigh S, Sezer K, Li L, Grafton-Reed C, Cuttall M. Recast and oxide formation in laser-drilled acute holes in CMSX-4 nickel single-crystal superalloy. *Proceedings of the Institution of Mechanical Engineers. Part B, Journal of Engineering Manufacture*, 2010, 224(7): 1005–1016
 17. Zheng C, Zhao K, Shen H, Zhao X, Yao Z. Crack behavior in ultrafast laser drilling of thermal barrier coated nickel superalloy. *Journal of Materials Processing Technology*, 2020, 282: 116678
 18. Méchain G, Couairon A, Franco M, Prade B, Mysyrowicz A. Organizing multiple femtosecond filaments in air. *Physical Review Letters*, 2004, 93(3): 035003
 19. Fu Y, Gao H, Chu W, Ni J, Xiong H, Xu H, Yao J, Zeng B, Liu W, Cheng Y, Xu Z, Chin S L. Control of filament branching in air by astigmatically focused femtosecond laser pulses. *Applied Physics B, Lasers and Optics*, 2011, 103(2): 435–439
 20. Eisenmann S, Pukhov A, Zigler A. Fine structure of a laser-plasma filament in air. *Physical Review Letters*, 2007, 98(15): 155002
 21. Kamali Y, Sun Q, Daigle J F, Azarm A, Bernhardt J, Chin S L J O C. Lens tilting effect on filamentation and filament-induced fluorescence. *Optics Communications*, 2009, 282(5): 950–954
 22. Goodwin P C. Evaluating optical aberrations using fluorescent microspheres: methods, analysis, and corrective actions. *Methods in Cell Biology*, 2013, 114: 369–385
 23. Das D K, Pollock T M. Femtosecond laser machining of cooling holes in thermal barrier coated CMSX4 superalloy. *Journal of Materials Processing Technology*, 2009, 209(15–16): 5661–5668

24. Uchtmann H, He C, Gillner A. High precision and high aspect ratio laser drilling: challenges and solutions. In: *Proceedings of Conference on High-Power Laser Materials Processing—Lasers, Beam Delivery, Diagnostics, and Applications V*. San Francisco: SPIE, 2016
25. Mincuzzi G, Faucon M, Kling R. Novel approaches in zero taper, fast drilling of thick metallic parts by ultra-short pulse laser. *Optics and Lasers in Engineering*, 2019, 118: 52–57



Manshi Wang received her B.S. degree in Physics from Nanjing Normal University, China, in 2019. From 2019 until now, she is pursuing a master's degree in Optical Engineering at Institute of Modern Optics, Nankai University, China. Her research focuses on ultrafast laser processing and laser-induced periodic surface structures.

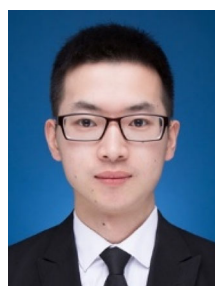

Zhiqiang Yu received his Bachelor's degree in Optoelectronic Information Science and Engineering from School of Optoelectronic Engineering, Changchun University of Science and Technology, China, in 2017. From September 2017 to June 2019, he received his M.S. degree in Optical Engineering from Institute of Modern Optics, School of Electronic Information Science and Engineering, Nankai University, China. From September 2019 to the present, he is pursuing a Ph.D. degree in Optical Engineering at Institute of Modern Optics, School of Electronic Information Science and Engineering, Nankai University. Currently, he engages in research on ultrafast optics and its applications.



Nan Zhang received his Ph.D. degree in Optical Engineering from Nankai University, China, in 2009. From 2009 to 2013, he was a lecturer in Nankai University; from 2013 to present, he is an associate professor in Institute of Modern Optics, Nankai University. His major research field is ultrafast laser-matter interaction, including the ultrafast thermodynamic evolution of femtosecond laser ablation, femtosecond laser induced periodic surface structures, and etc.



Weiwei Liu received his Ph.D. degree in Physics from Laval University, Québec, QC, Canada, in 2005. Since 2007, he has been working as a full professor with Institute of Modern Optics, Nankai University, China. His main research interests include ultrafast laser optics, THz science and technology, and nonlinear optics.